

AD-A074 046

ADVISORY GROUP FOR AEROSPACE RESEARCH AND DEVELOPMENT--ETC F/G 21/5
TECHNICAL EVALUATION REPORT OF THE SPECIALISTS' MEETING ON CHAR--ETC(U)
JUL 79 J M DRAPIER, M H HIRSCHBERG

UNCLASSIFIED


AGARD-AR-130

NL

| OF |
AD
A074046



END
DATE
FILMED
10-79
DDC

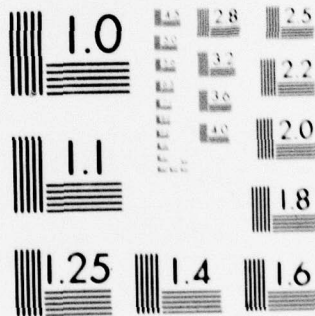

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

AGARD-AR-130

AGARD-AR-130

AGARD

ADVISORY GROUP FOR AEROSPACE RESEARCH & DEVELOPMENT

7 RUE ANCELLE 92200 NEUILLY SUR SEINE FRANCE

AD A 074046

AGARD ADVISORY REPORT No. 130

Technical Evaluation Report

of the

Specialists' Meeting

on

Characterization of Low Cycle High
Temperature Fatigue By The Strainrange
Partitioning Method

by

J.M.Drapier and M.H.Hirschberg

LEVEL

DDC FILE COPY

NORTH ATLANTIC TREATY ORGANIZATION



DISTRIBUTION STATEMENT A

Approved for public release
Distribution Unlimited

DISTRIBUTION AND AVAILABILITY
ON BACK COVER

SEP 20 1979

79 09 17

0473

NORTH ATLANTIC TREATY ORGANIZATION
ADVISORY GROUP FOR AEROSPACE RESEARCH AND DEVELOPMENT
(ORGANISATION DU TRAITE DE L'ATLANTIQUE NORD)

9
AGARD Advisory Report No. 130

6
TECHNICAL EVALUATION REPORT

of the

SPECIALISTS' MEETING

on

CHARACTERIZATION OF LOW CYCLE HIGH TEMPERATURE FATIGUE

BY THE STRAINRANGE PARTITIONING METHOD

by

10
J.M. Drapier and M.H. Hirschberg

12
15p.

ACQUISITION FOR	
NTIS GRA&I	<input checked="" type="checkbox"/>
DDC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist.	Avail and/or special
A	

THE MISSION OF AGARD

The mission of AGARD is to bring together the leading personalities of the NATO nations in the fields of science and technology relating to aerospace for the following purposes:

- Exchanging of scientific and technical information;
- Continuously stimulating advances in the aerospace sciences relevant to strengthening the common defence posture;
- Improving the co-operation among member nations in aerospace research and development;
- Providing scientific and technical advice and assistance to the North Atlantic Military Committee in the field of aerospace research and development;
- Rendering scientific and technical assistance, as requested, to other NATO bodies and to member nations in connection with research and development problems in the aerospace field;
- Providing assistance to member nations for the purpose of increasing their scientific and technical potential;
- Recommending effective ways for the member nations to use their research and development capabilities for the common benefit of the NATO community.

The highest authority within AGARD is the National Delegates Board consisting of officially appointed senior representatives from each member nation. The mission of AGARD is carried out through the Panels which are composed of experts appointed by the National Delegates, the Consultant and Exchange Programme and the Aerospace Applications Studies Programme. The results of AGARD work are reported to the member nations and the NATO Authorities through the AGARD series of publications of which this is one.

Participation in AGARD activities is by invitation only and is normally limited to citizens of the NATO nations.

The content of this publication has been reproduced directly from material supplied by AGARD or the authors.

Published July 1979

Copyright © AGARD 1979
all Rights Reserved

ISBN 92-835-1328-2



Printed by Technical Editing and Reproduction Ltd
Harford House, 7-9 Charlotte St, London, W1P 1HD

PREFACE

The AGARD Structures and Materials Panel has had a long and active interest in researching subjects that are of a critical nature and of common interest to the NATO community. In keeping with this tradition, the Panel, in the Spring of 1971 deemed it highly advisable to initiate specific activities in the area of low cycle high temperature fatigue (LCHTF).

At the Fall 1972 S&M Panel Meeting, Mr. Drapier, who was charged by AGARD with the coordination of the various activities on this subject, submitted a document entitled "Ad Hoc Group on Low Cycle High Temperature Fatigue - Status Report" (AGARD R-604), which reviewed the LCHTF work being carried out by the NATO nation laboratories interested in this problem. In the fall of 1973, Mr. Drapier presented to the S&M Panel his in-depth report entitled "Survey of Activities in the Field of Low Cycle High Temperature Fatigue". This document was published as AGARD R-618 in February 1974.

Through the continuing efforts of Mr. Drapier, supported by this Panel, AGARD has published a volume containing the papers presented at the Specialists' Meeting on Low Cycle High Temperature Fatigue (AGARD-CP-155) held in April 1974. At this meeting, experts were invited to provide replies to a number of questions raised by the organizers; each subject was introduced by a paper, the purpose of which was to survey the problem areas associated with that subject and to orient and focus the subsequent discussion.

One of the conclusions of the above noted Specialists' Meeting was the recognition of the need for reliable life prediction methods that are applicable to LCHTF gas turbine components. It was in the spring of 1975 that Mr. Hirschberg presented a pilot paper suggesting a cooperative testing program aimed at evaluating the ability of the Strainrange Partitioning Method to predict life in the creep-fatigue range. Messrs Hirschberg and Drapier were designated coordinators for this program. The laboratories surveyed in AGARD R-618 were then invited to participate. Nineteen laboratories in five countries chose to participate, each testing its own materials of interest under its own laboratory conditions so that the results obtained would provide validation for a wide range of materials and insure maximum usefulness to each of the participating laboratories. The culmination of this evaluation program was the Specialists' meeting which brought together these investigators for the purpose of sharing their laboratory testing experiences, permitting an in-depth evaluation of the Strainrange Partitioning method, and providing maximum exposure to the findings and recommendations of this distinguished body of specialists.

This Technical Evaluation Report of the Specialists' Meeting analyzes the present state of understanding of the method of Strainrange Partitioning for analysis and prediction of low-cycle high-temperature fatigue life. Recommendations for future activities which would be appropriate and valuable in this expanding area of life prediction are also included. Together with the Conference Proceedings, AGARD CP-243 published in August 1978, it represents a major contribution to this technology which is of vital concern to the NATO nations.

George C. Deutsch
Chairman, Sub-Committee on
High Temperature Materials

CONTENTS

	Page
PREFACE	iii
1. BACKGROUND	1
2. PROGRAMME OBJECTIVES	1
3. SURVEY OF THE PROGRAMME ORGANIZATION	1
4. RESULTS OF THE PROGRAMME	2
5. CONCLUSIONS AND RECOMMENDATIONS	3
6. ACKNOWLEDGEMENTS	3
7. REFERENCES	3
APPENDIX A1	5

1

COOPERATIVE TESTING PROGRAMME ON STRAINRANGE
PARTITIONING
EVALUATION REPORT
by

J.M.DRAPIER

Fabrique Nationale Herstal
Formetal Division
4400 Herstal, Belgium
(European Coordinator)

Marvin H.HIRSCHBERG

NASA Lewis Research Center
Cleveland, Ohio, USA
(U.S. Coordinator)

1. BACKGROUND

The AGARD Structures and Materials Panel has had a long and active interest in researching subjects that are of a critical nature and of common interest to the NATO community. In keeping with this tradition, the Panel, in the Spring of 1971 deemed it advisable to initiate specific activities in the area of low cycle high temperature fatigue (LCHTF).

This resulted in an AGARD publication (1) reviewing the LCHTF work being carried out by the laboratories in the various nations interested in this problem.

Through the continuing efforts supported by this Panel, AGARD published the proceedings of a Specialist's Meeting on LCHTF (2). One of the conclusions of this conference was the recognition of the need for more reliable life prediction methods that are applicable to LCHTF of gas turbine components. As a result, and following a suggestion made by Mr. H.HIRSCHBERG in the spring of 1975, The Structures and Materials Panel decided to support the cooperative evaluation programme we are reviewing in this report.

2. PROGRAMME OBJECTIVES

The basic objective of the cooperative programme was to evaluate the ability of the Strainrange Partitioning (SRP) method to first correlate the creep-fatigue behavior of gas turbine materials, and then to predict the creep-fatigue lives of laboratory specimens subjected to complex cycling conditions.

The programme, by its very nature, would provide a reference body of high temperature creep-fatigue data that would enable future use by researchers in the evaluation of SRP or other LCHTF predictive techniques.

It was also suggested at the beginning of this programme that each of the participants generate and record any additional creep-fatigue data that would permit them to make a direct comparison between SRP and any other life prediction method that they are currently using or are interested in themselves developing.

3. SURVEY OF THE PROGRAMME ORGANIZATION

3.1. Following invitations made to the laboratories previously surveyed (1), 16 laboratories in 5 countries (7 U.S. ; 5 U.K., 2 French, 1 German and 1 Italian) agreed to participate in the programme.

3.2. One important aspect of this agreement was that each participant test its own materials of interest under its own laboratory conditions so that the results generated would provide validation for a wide range of materials and would insure maximum usefulness to each of the participating laboratories.

3.3. The materials tested included a number of cast, wrought and P/M nickel-base superalloys, titanium and copper-base alloys as well as steels. Most of them are used or are intended for use in gas turbine components, such as blades and discs, for aircraft or land-based applications.

3.4. The programme starting in the fall of 1975 was organized and conducted by these authors, coordinating the activities among the U.S. and the European participants respectively.

3.5. The culmination of this programme was the Specialist's Meeting discussed herein which brought together the various investigators with the objective of sharing their findings to pursue an in-depth evaluation of the SRP method.

3.6. One important, and probably decisive, tool used by the coordinators to guarantee the success of this activity was the organization of interim programme review meetings. These meetings provided the opportunity to the investigators for critical in-depth interchanges of ideas, concerns, testing techniques, as well as the evaluation of test results.

Three separate interim meetings were held in the U.S. as well as in Europe, Mr. M.H. HIRSCHBERG, one of the developers of the SRP method, attended all of these meetings.

4. RESULTS OF THE PROGRAMME

In order to evaluate the results of the cooperative programme, it must be kept in mind that its main objective, recalled in Section 2, corresponds to the first, very necessary step in the evaluation of a life prediction approach: the evaluation of the ability of this method to predict the life of specimens subjected to complex loading from specimen data obtained from simple tests. One could hope to obtain reliable life predictions for engine components if it is not possible to reliably predict first the lives of well controlled laboratory specimens

4.1. Data tabulation : All of the data collected from the participating laboratories were tabulated in a common format and appear in the Appendix to the Proceedings of the Specialist's Meeting (3). In addition to the creep-fatigue test conditions and data, there are also included chemical compositions, material processing and heat-treatment, and the conventional mechanical properties for each of the alloys tested.

In this form, these tabulations represent an extremely valuable body of data covering a variety of engineering alloys so that future analysis and interpretations can be made with a minimum of effort and a maximum of reliability.

4.2. Evaluation of the SRP method : Such an evaluation could be made by answering to the following questions : *

- * Does the SRP method work in correlating, and possibly extrapolating, LCHTF data generated on laboratory specimens ?

- * How does the SRP method compare to other techniques ?

- * What are its specific advantages or disadvantages ?

- * Are there important gaps at this point in our understanding

of this approach ?

Trying to answer these questions, the following comments can be made :

-a. Through the various papers presented, and the discussions held at the Conference, the general consensus of the investigators involved in the programme appears to be positive and in agreement that the SRP method is a significant step forward in LCHTF life prediction.

Accordingly, designers of engine components express their intent to continue to work with the SRP method for the purpose of predicting the initiation phase of creep-fatigue cracking.

-b. While the application of the ductility criterion requires more extensive validation, the use of the present ductility-normalized (DN) SRP relationships appears to be a good realistic way to predict creep-fatigue life relationships in the absence of cyclic data.

-c. A single method such as SRP is not expected to apply over every set of circumstances involving variables such as material, temperature range, environment and other testing conditions which can give rise to different failure mechanisms. In this respect, it is made clear that the SRP method, in its present form, is only intended for use under crack initiation conditions.

As regards the nickel-base superalloys, or more generally materials which may have a very low fracture toughness, it becomes very important to separate crack initiation and propagation phases from each other.

-d. The numerous data generated in this programme clearly show that, for nickel-base superalloys, the DN-SRP basic life relationships, PP, PC, CP and CC, lie very close together, in some cases collapsing into one line, closer than for materials such as stainless steels and low alloy steels which were mainly investigated up to now.

-e. Despite this particular behaviour of the investigated nickel-base superalloys during LCHTF testing, the usefulness of SRP in establishing bounds of life is stated to be still valid.

On the other hand, the use of SRP appears not to require any more prior information (and in some instances much less) than other predictive methods.

From the results presented at the Conference, it was not possible to identify any advantages or improvement in life predictions in using alternative predictive methods such as the simple stress correlation or a continuous damage accumulation approach.

-f. Some problems arise when applying the SRP method to cases involving small

inelastic strains and long lives. In particular, partitioning of the corresponding narrow hysteresis loops is reported as being a concern. The major problem is simply one of not being able to accurately identify the exact magnitude of the inelastic strainrange as well as the creep strain present in the hysteresis loop. However, this is a problem with some of the other approaches as well.

-g. The SRP method, in its present form, appears to require some modification in order to handle mean stress effects. Tentatively, it was proposed that, due to the very close SRP lines for the nickel-base superalloys, a mean stress effect could give rise to an apparent inversion of life relationships.

-h. Attempts are also reported to correlate the types of cycling and the modes of cracking.

Generally, PP and PC tests give rise to transgranular cracking only, whereas CP cracking was almost entirely intergranular and CC cracking was mixed. However, further investigations appear to be required in order to substantiate these correlations as well as to clarify the environmental effects.

5. CONCLUSIONS AND RECOMMENDATIONS

5.1. From the answers to the questions posed in the previous Section, it can be concluded that the cooperative evaluation programme has succeeded in achieving its tasks.

5.2. The results of this programme allow us also to identify some topics which could be addressed to the Panel for possible future activities in the field of LCHTF :

-a. There is a general interest in the influence of mean stress on low cycle fatigue behaviour, and some critical experiments would be valuable in this area. A systematic study would certainly be required to separate the effects of strain type and mean stress, and so expand the applicability of the SRP method.

-b. Difficulties associated with the partitioning of narrow hysteresis loops involving small inelastic strains and long lives should be resolved. The proponents of the SRP method are attempting to overcome this difficulty by formulating the method in terms of total strains rather than the inelastic strains. It is however, recognized that the data base required to develop this modified formulation of SRP is presently lacking.

-c. Looking at the predictive nature of the SRP method, attempts to generate extrapolation data for superalloys, as it has already been made for low alloy steels and stainless steels, would certainly be valuable.

-d. Further investigations would also be required in order to increase the understanding of the correlations existing between the modes of cracking and the types of cycling including the environmental effects.

5.3. Finally, from a more general view-point and returning to the programme survey given in section 3, these authors feel that this activity could serve as a reference to the Panel for the organization and fulfillment of future similar cooperative actions involving a number of partners among the various NATO nations.

6. ACKNOWLEDGEMENTS

Arriving at the completion of their tasks, the authors of this report wish to thank, for themselves and also on behalf of the Panel, all of the participants in the programme for their successful efforts in meeting the timetable established from the beginning of this 3 years activity. The success of the Specialist's Meeting, and therefore of the whole programme, is the direct result of their fruitful cooperation allowing their data and conclusions to be made available in convenient time.

7. REFERENCES

- (1) DRAPIER J.M. "Survey of Activities in the Field of Low-Cycle High Temperature Fatigue" :
Critical Report AGARD - R - 618
- (2) AGARD Conference Proceedings of the "Specialist's Meeting on Low Cycle High Temperature Fatigue" AGARD - CP - 155
- (3) AGARD Conference Proceedings of the Specialist's Meeting on "Characterization of Low Cycle High Temperature Fatigue by the Strainrange Partitioning Method".
AGARD - CP - 243.

APPENDIX A1

The contents of this appendix are some additional tabulations of Creep-Fatigue test data that were collected after the publication of AGARD-CP-243. The Chemical Compositions, Processing & Heat Treatment information, and the Mechanical Properties data appropriate to these additional data can be found in Tables I, II, and III of Appendix A1 in AGARD-CP-243.

ERRATA

AGARD Conference Proceedings No 243, page 16-14

In Table 3, the axial components of strain only must be multiplied by two to be correct. The torsional components of strain are correct as reported.

These changes affect the entries in columns 3, 4, 5, 7 and 10 only for specimens numbers A-7, A-8, A-9, A-12, A-13, A-14, A-15, N-1, N-5, N-9, N-2, N-6 and N-10.

The axial and biaxial data ($R=0,2$) plotted in Figs. 9, 10, 11 and 12 are also affected, as are the constants in equations 16 and 17.

Questions of clarification should be addressed to the author, Professor S.Y. Zamrik.

PRECEDING PAGE BLANK

TABLE IV: CREEP-FATIGUE DATA (CONTINUED)

LABORATORY: NPL
MATERIAL: INCOLOY 738LC

RATE DATA & STRESSES

SPEC NO	TEST TYPE	TEMP-C	RATE DATA (HALF-LIFE VALUES)			STRESSES (HALF-LIFE VALUES) MPa			RELAXATION			CYCLIC STRAIN		
			FREQ	STRAIN-RATE-S/SEC	HOLD-TIME-SEC	TEN	COMP	MAX	TEN	COMP	MAX	TEN	COMP	HARDENING %
DCH56	HRSC	750/750	5.7E-01	8.0E-01	8.0E-01	0	0	410.0	572.0	982.0	0.0	0.0	0.0	-7.50
DCH76	HRSC	750/750	5.0E-01	1.0E-01	1.0E-01	0	0	691.0	794.0	1485.0	0.0	0.0	0.0	-1.00
DCH30	CHSC	850/850	3.3E-03	8.0E-01	8.0E-01	0	300.0	773.0	408.0	1181.0	0.0	132.0	0.0	-5.00
DCH35	THSC	850/850	3.2E-03	8.0E-01	8.0E-01	300.0	0	294.0	749.0	1043.0	110.0	0.0	0.0	-15.00
DCH53	THSC	850/850	3.6E-03	8.0E-01	8.0E-01	300.0	0	275.0	734.0	1013.0	110.0	0.0	0.0	-9.50
DCH90	BCCR	750/750	6.6E-03	8.0E-01	8.0E-01	75.0	75.0	533.0	621.0	1154.0	0.0	0.0	0.0	--

STRAINS & FAILURE DATA

SPEC NO	STRAIN RANGES (HALF-LIFE VALUES) %			FAILURE DATA-CYCLES			TF-HRS		
	TOTAL	EL	IN	PP	PC	CP	CC	NO	NE
DCH56	0.700	0.690	0.011	0.011	0.000	0.000	0.000	6200	13100
DCH76	1.000	0.922	0.078	0.078	0.000	0.000	0.000	180	282
DCH30	1.000	0.730	0.270	0.150	0.121	0.000	0.000	--	36
DCH35	1.000	0.722	0.278	0.171	0.000	0.108	0.000	420	625
DCH53	1.000	0.730	0.270	0.170	0.000	0.100	0.000	440	610
DCH90	1.000	0.665	0.135	0.071	0.000	0.000	0.064	350	500

TABLE IV: CREEP-FATIGUE DATA (CONTINUED)

LABORATORY: ROLLS-ROYCE, LTD.
MATERIAL: WASPALOY

RATE DATA & STRESSES

SPEC NO	TEST TYPE	TEMP-C	FREQ HZ	RATE DATA (HALF-LIFE VALUES)			STRESS-RANGE			STRESSES (HALF-LIFE VALUES) MPa			CYCLIC STRAIN	HARDENING &
				STRAIN-RATE-X/SEC	MO	TIME-SEC	MIN	MAX	MIN	MAX	MIN	MAX		
BASELINE SFP TESTS														
SP34	HRSC	700/700	1.3E 00	9.0E 00	7.0E 00	0	0	904.6	976.1	1860.7	0.0	0.0	--	--
SP35	HRSC	700/700	1.3E 00	7.1E 00	7.1E 00	0	0	847.2	878.6	1725.8	0.0	0.0	--	--
SP33	HRSC	700/700	1.3E 00	3.6E 00	3.6E 00	0	0	698.8	714.5	1413.3	0.0	0.0	--	--
SP6	HRSC	700/700	6.2E-01	1.8E 00	1.8E 00	0	0	747.6	778.7	1526.3	0.0	0.0	--	--
SP50	THSC	700/700	--	2.3E 00	2.0E 00	900.0	0	991.4	1162.3	2153.7	419.4	0.0	--	--
SP24	TCCR	700/700	--	3.7E-01	6.6E-01	720.0	0	608.2	1016.6	1524.8	0.0	0.0	--	--
SP21	CCCR	700/700	--	1.3E 00	9.0E-01	2700.0	0	1106.4	713.3	1619.7	0.0	0.0	--	--
SP17	BCCR	700/700	--	8.1E-01	7.3E-01	840.0	240.0	640.6	838.5	1479.1	0.0	0.0	--	--
SP43	BCCR	700/700	--	5.1E-01	4.3E-01	120.0	870.0	574.4	373.1	1047.5	0.0	0.0	--	--
COMPLEX TESTS														
SP2	UCCR	700/700	--	5.7E-01	6.6E-01	420.0	900.0	652.7	717.6	1370.2	0.0	0.0	--	--
SP19	UCCR	700/700	--	6.0E-01	9.3E-01	120.0	1800.0	901.3	699.6	1600.9	0.0	0.0	--	--
SP44	UCCR	700/700	--	5.5E-01	5.2E-01	90.0	60.0	596.0	631.4	1227.4	0.0	0.0	--	--

STRAINS & FAILURE DATA

SPEC NO	STRAIN-RANGES (HALF-LIFE VALUES) %				FAILURE DATA-CYCLES				TF-HRS			
	TOTAL	EL	IN	PR	PC	CP	CC	N0		N1	N2	
BASELINE SRP TESTS												
SP34	3.610	1.530	2.080	2.080	0.000	0.000	0.000	--	--	--	318	0.07
SP35	2.840	1.260	1.580	1.580	0.000	0.000	0.000	--	--	--	645	0.14
SP33	1.440	1.000	0.440	0.440	0.000	0.000	0.000	--	--	--	3404	0.75
SP6	1.440	1.020	0.420	0.420	0.000	0.000	0.000	--	--	--	2718	1.21
SP50	4.510	1.250	2.760	2.030	0.000	0.730	0.000	--	--	--	57	14.75
SP24	1.460	0.590	0.670	0.250	0.000	0.620	0.000	--	--	--	62	40.37
SP21	2.890	1.210	1.690	0.620	1.060	0.000	0.000	--	--	--	96	82.00
SP17	2.940	1.000	1.940	0.610	0.000	0.000	1.330	--	--	--	76	31.75
SP43	1.280	0.700	0.580	0.160	0.000	0.000	0.420	--	--	--	710	469.70
COMPLEX TESTS												
SP2	1.530	0.930	0.600	0.200	0.000	0.220	0.180	--	--	--	100	150.00
SP19	3.120	1.050	2.070	0.600	0.000	0.210	1.280	--	--	--	54	150.00
SP44	1.380	0.860	0.520	0.190	0.000	0.050	0.280	--	--	--	1840	143.70

LABORATORY: DPVLE
MATERIAL: TIAL6V4

RATE DATA & STRESSES																	
SPEC NO	TEST TYPE	TEMP-C	FREQ HZ	RATE DATA(HALF-LIFE VALUES)				STRESSES(HALF-LIFE VALUES) MPa									
				TEMP	CONP	STRAIN-RATE-1/SEC	HOLD TIME-SEC	TEMP	CONP	TEMP	CONP	TEMP	CONP	RELAXATION	CYCLIC STRAIN	HARDENING &	
		TEMP/CONP		TEMP	CONP	TEMP	CONP	TEMP	CONP	TEMP	CONP	TEMP	CONP	TEMP	CONP	TEMP	CONP
199/01	HFSC	450/450	3.0E-01	6.5E-01	6.1E-01	0	0	527.9	507.0	1034.9	0.0	0.0	0.0	0.0	0.0	-3.40	
199/03	HFSC	450/450	3.0E-01	6.4E-01	5.6E-01	0	0	509.6	520.0	1029.6	0.0	0.0	0.0	0.0	0.0	-2.90	
199/05	HFSC	450/450	3.0E-01	5.9E-01	5.8E-01	0	0	492.6	462.8	955.4	0.0	0.0	0.0	0.0	0.0	-2.20	
195/13	UCCR	450/450	1.0E-01	7.0E-01	6.8E-01	0.5	7.8E-01	714.3	412.7	1127.1	0.0	0.0	0.0	0.0	0.0	-0.37	
194/14	UCCR	450/450	1.0E-01	6.2E-01	5.9E-01	0.5	136E-01	740.3	275.3	1015.5	0.0	0.0	0.0	0.0	0.0	-1.02	
195/05	UCCR	450/450	1.0E-01	6.2E-01	7.1E-01	0.6	96E-01	632.8	377.6	1010.4	0.0	0.0	0.0	0.0	0.0	-8.33	
195/04	UCCR	450/450	1.0E-01	5.4E-01	5.7E-01	2.0	84E-01	625.8	351.0	976.8	0.0	0.0	0.0	0.0	0.0	-7.03	
194/19	UCCR	450/450	1.0E-01	5.7E-01	5.8E-01	3.0	21E-01	618.2	351.7	969.9	0.0	0.0	0.0	0.0	0.0	-6.10	
194/11	UCCR	450/450	1.0E-01	5.0E-01	4.9E-01	1.0	16E-01	623.1	314.1	937.3	0.0	0.0	0.0	0.0	0.0	-9.00	
194/21	UCCR	450/450	1.0E-01	4.9E-01	5.0E-01	15.0	4E-01	563.0	370.3	933.3	0.0	0.0	0.0	0.0	0.0	-5.60	
199/13	UCCR	450/450	1.0E-01	5.2E-01	4.8E-01	324.0	0.5	334.4	731.8	1066.3	0.0	0.0	0.0	0.0	0.0	-3.55	
199/12	UCCR	450/450	1.0E-01	4.7E-01	4.5E-01	360.0	0.5	290.0	780.3	1070.3	0.0	0.0	0.0	0.0	0.0	4.00	
199/10	BCCR	450/450	1.0E-01	5.7E-01	5.5E-01	21.0	30.0	528.2	486.8	1015.0	0.0	0.0	0.0	0.0	0.0	-5.58	
190/13	BCCR	450/450	1.0E-01	5.5E-01	5.9E-01	10.8	24.0	537.2	490.7	1027.9	0.0	0.0	0.0	0.0	0.0	-6.31	
199/11	BCCR	450/450	1.0E-01	4.8E-01	4.9E-01	15.0	30.0	516.8	415.1	932.0	0.0	0.0	0.0	0.0	0.0	-4.00	
199/19	ECCR	450/450	1.0E-01	4.5E-01	4.6E-01	4.2	8.4	505.2	409.3	914.5	0.0	0.0	0.0	0.0	0.0	-7.60	
195/18	BCCR	450/450	1.0E-01	4.5E-01	4.3E-01	6.0	6.0	480.3	442.4	922.8	0.0	0.0	0.0	0.0	0.0	-1.50	

SPEC NO	STRAIN RANGES (HALF-LIFE VALUES), %				FAILURE DATA-CYCLES				T ₁ -HRS
	TOTAL	EL	IN	CP	NI	N5	NF		
199/01	0.932	0.518	0.074	0.000	0.000	3800	5016	4.65	
199/03	0.964	0.884	0.080	0.000	0.000	5110	7315	6.77	
199/05	0.923	0.873	0.051	0.000	0.000	7320	7717	7.13	
199/13	1.465	1.051	0.414	0.123	0.116	210	284	448.95	
199/14	1.230	0.989	0.241	0.091	0.078	292	364	1127.90	
199/05	1.232	0.972	0.260	0.034	0.036	445	546	363.45	
199/04	1.097	0.937	0.160	0.026	0.052	595	710	432.03	
199/19	1.061	0.867	0.194	0.029	0.054	870	1044	218.33	
199/11	0.953	0.842	0.111	0.036	0.059	971	1087	387.45	
199/21	0.959	0.858	0.101	0.029	0.065	1800	2117	117.66	
199/13	1.074	0.890	0.184	0.082	0.067	2300	3378	240.82	
199/12	0.935	0.816	0.119	0.052	0.034	4212	4549	474.66	
199/10	1.128	0.908	0.221	0.118	0.103	1210	1332	44.17	
199/13	1.059	0.766	0.333	0.180	0.153	1215	1437	228.60	
199/11	0.903	0.793	0.110	0.051	0.051	2424	2603	192.00	
199/19	0.759	0.725	0.074	0.038	0.036	3900	4751	124.68	
199/18	0.814	0.755	0.059	0.000	0.036	4800	5293	105.50	

REPORT DOCUMENTATION PAGE			
1. Recipient's Reference	2. Originator's Reference AGARD-AR-130	3. Further Reference ISBN 92-835-1328-2	4. Security Classification of Document UNCLASSIFIED
5. Originator Advisory Group for Aerospace Research and Development North Atlantic Treaty Organization 7 rue Ancelle, 92200 Neuilly sur Seine, France			
6. Title TECHNICAL EVALUATION REPORT of the SPECIALISTS' MEETING on CHARACTERIZATION OF LOW CYCLE HIGH TEMPERATURE FATIGUE BY THE STRAINRANGE PARTITIONING METHOD			
7. Presented at			
8. Author(s)/Editor(s) J.M.Drapier* M.H.Hirschberg†			9. Date July 1979
10. Author's/Editor's Address * Fabrique Nationale Herstal Formetal Division 4400 Herstal, Belgium. † NASA Lewis Research Center Cleveland, Ohio, USA.			11. Pages 14
12. Distribution Statement This document is distributed in accordance with AGARD policies and regulations, which are outlined on the Outside Back Covers of all AGARD publications.			
13. Keywords/Descriptors Fatigue life High temperature tests Fatigue strength Predictions Fatigue (materials) Strain			
15. Abstract This Technical Evaluation Report of the Specialists' Meeting analyzes the present state of understanding of the method of Strainrange Partitioning for analysis and prediction of low-cycle high-temperature fatigue life. Recommendations for future activities which would be appropriate and valuable in this expanding area of life prediction are also included. Together with the Conference Proceedings, AGARD CP-243 published in August 1978, it represents a major contribution to this technology which is of vital concern to the NATO nations. This Advisory Report was sponsored by the Structures and Materials Panel of AGARD.			

<p>AGARD Advisory Report No.130 Advisory Group for Aerospace Research and Development, NATO</p> <p>TECHNICAL EVALUATION REPORT of the SPECIALISTS' MEETING on CHARACTERIZATION OF LOW CYCLE HIGH TEMPERATURE FATIGUE BY THE STRAINRANGE PARTITIONING METHOD by J.M.Drapier and M.H.Hirschberg Published July 1979 14 pages</p> <p>This Technical Evaluation Report of the Specialists' Meeting analyzes the present state of understanding of the methods of Strainrange Partitioning for analysis and prediction of low-cycle high-temperature fatigue life. Recommendations for future activities which would be</p> <p>P.T.O</p>	<p>AGARD-AR-130</p> <p>Fatigue life Fatigue strength Fatigue (materials) High temperature tests Prediction Strain</p>	<p>AGARD Advisory Report No.130 Advisory Group for Aerospace Research and Development, NATO</p> <p>TECHNICAL EVALUATION REPORT of the SPECIALISTS' MEETING on CHARACTERIZATION OF LOW CYCLE HIGH TEMPERATURE FATIGUE BY THE STRAINRANGE PARTITIONING METHOD by J.M.Drapier and M.H.Hirschberg Published July 1979 14 pages</p> <p>This Technical Evaluation Report of the Specialists' Meeting analyzes the present state of understanding of the methods of Strainrange Partitioning for analysis and prediction of low-cycle high-temperature fatigue life. Recommendations for future activities which would be</p> <p>P.T.O</p>	<p>AGARD-AR-130</p> <p>Fatigue life Fatigue strength Fatigue (materials) High temperature tests Prediction Strain</p>
<p>AGARD Advisory Report No.130 Advisory Group for Aerospace Research and Development, NATO</p> <p>TECHNICAL EVALUATION REPORT of the SPECIALISTS' MEETING on CHARACTERIZATION OF LOW CYCLE HIGH TEMPERATURE FATIGUE BY THE STRAINRANGE PARTITIONING METHOD by J.M.Drapier and M.H.Hirschberg Published July 1979 14 pages</p> <p>This Technical Evaluation Report of the Specialists' Meeting analyzes the present state of understanding of the methods of Strainrange Partitioning for analysis and prediction of low-cycle high-temperature fatigue life. Recommendations for future activities which would be</p> <p>P.T.O</p>	<p>AGARD-AR-130</p> <p>Fatigue life Fatigue strength Fatigue (materials) High temperature tests Prediction Strain</p>	<p>AGARD Advisory Report No.130 Advisory Group for Aerospace Research and Development, NATO</p> <p>TECHNICAL EVALUATION REPORT of the SPECIALISTS' MEETING on CHARACTERIZATION OF LOW CYCLE HIGH TEMPERATURE FATIGUE BY THE STRAINRANGE PARTITIONING METHOD by J.M.Drapier and M.H.Hirschberg Published July 1979 14 pages</p> <p>This Technical Evaluation Report of the Specialists' Meeting analyzes the present state of understanding of the methods of Strainrange Partitioning for analysis and prediction of low-cycle high-temperature fatigue life. Recommendations for future activities which would be</p> <p>P.T.O</p>	<p>AGARD-AR-130</p> <p>Fatigue life Fatigue strength Fatigue (materials) High temperature tests Prediction Strain</p>

<p>appropriate and valuable in this expanding area of life prediction are also included. Together with the Conference Proceedings, AGARD CP-243 published in August 1978, it represents a major contribution to this technology which is of vital concern to the NATO nations.</p> <p>This Advisory Report was sponsored by the Structures and Materials Panel of AGARD.</p> <p>ISBN 92-835-1328-2</p>	<p>appropriate and valuable in this expanding area of life prediction are also included. Together with the Conference Proceedings, AGARD CP-243 published in August 1978, it represents a major contribution to this technology which is of vital concern to the NATO nations.</p> <p>This Advisory Report was sponsored by the Structures and Materials Panel of AGARD.</p> <p>ISBN 92-835-1328-2</p>
<p>appropriate and valuable in this expanding area of life prediction are also included. Together with the Conference Proceedings, AGARD CP-243 published in August 1978, it represents a major contribution to this technology which is of vital concern to the NATO nations.</p> <p>This Advisory Report was sponsored by the Structures and Materials Panel of AGARD.</p> <p>ISBN 92-835-1328-2</p>	<p>appropriate and valuable in this expanding area of life prediction are also included. Together with the Conference Proceedings, AGARD CP-243 published in August 1978, it represents a major contribution to this technology which is of vital concern to the NATO nations.</p> <p>This Advisory Report was sponsored by the Structures and Materials Panel of AGARD.</p> <p>ISBN 92-835-1328-2</p>

AGARD

NATO  OTAN

**7 RUE ANCELLE · 92200 NEUILLY-SUR-SEINE
FRANCE**

Telephone 745.08.10 · Telex 610176

**DISTRIBUTION OF UNCLASSIFIED
AGARD PUBLICATIONS**

AGARD does NOT hold stocks of AGARD publications at the above address for general distribution. Initial distribution of AGARD publications is made to AGARD Member Nations through the following National Distribution Centres. Further copies are sometimes available from these Centres, but if not may be purchased in Microfiche or Photocopy form from the Purchase Agencies listed below.

NATIONAL DISTRIBUTION CENTRES

BELGIUM

Coordonnateur AGARD - VSL
Etat-Major de la Force Aérienne
Quartier Reine Elisabeth
Rue d'Evere, 1140 Bruxelles

CANADA

Defence Scientific Information Service
Department of National Defence
Ottawa, Ontario K1A 0Z2

DENMARK

Danish Defence Research Board
Østerbrogades Kaserne
Copenhagen Ø

FRANCE

O.N.E.R.A. (Direction)
29 Avenue de la Division Leclerc
92 Châtillon sous Bagneux

GERMANY

Zentralstelle für Luft- und Raumfahrt-
dokumentation und -information
c/o Fachinformationszentrum Energie,
Physik, Mathematik GmbH
Kernforschungszentrum
7514 Eggenstein-Leopoldshafen 2

GREECE

Hellenic Air Force General Staff
Research and Development Directorate
Holargos, Athens, Greece

ICELAND

Director of Aviation
c/o Flugrad
Reykjavik

ITALY

Aeronautica Militare
Ufficio del Delegato Nazionale all'AGARD
3, Piazzale Adenauer
Roma/EUR

LUXEMBOURG

See Belgium

NETHERLANDS

Netherlands Delegation to AGARD
National Aerospace Laboratory, NLR
P.O. Box 126
Delft

NORWAY

Norwegian Defence Research Establishment
Main Library
P.O. Box 25
N-2007 Kjeller

PORTUGAL

Direcção do Serviço de Material
da Força Aérea
Rua da Escola Politécnica 42
Lisboa
Attn: AGARD National Delegate

TURKEY

Department of Research and Development (ARGE)
Ministry of National Defence, Ankara

UNITED KINGDOM

Defence Research Information Centre
Station Square House
St. Mary Cray
Orpington, Kent BR5 3RE

UNITED STATES

National Aeronautics and Space Administration (NASA)
Langley Field, Virginia 23365
Attn: Report Distribution and Storage Unit

THE UNITED STATES NATIONAL DISTRIBUTION CENTRE (NASA) DOES NOT HOLD
STOCKS OF AGARD PUBLICATIONS, AND APPLICATIONS FOR COPIES SHOULD BE MADE
DIRECT TO THE NATIONAL TECHNICAL INFORMATION SERVICE (NTIS) AT THE ADDRESS BELOW.

PURCHASE AGENCIES

Microfiche or Photocopy

National Technical
Information Service (NTIS)
5285 Port Royal Road
Springfield
Virginia 22151, USA

Microfiche

Space Documentation Service
European Space Agency
10, rue Mario Nikis
75015 Paris, France

Microfiche

Technology Reports
Centre (DTI)
Station Square House
St. Mary Cray
Orpington, Kent BR5 3RF
England

Requests for microfiche or photocopies of AGARD documents should include the AGARD serial number, title, author or editor, and publication date. Requests to NTIS should include the NASA accession report number. Full bibliographical references and abstracts of AGARD publications are given in the following journals:

Scientific and Technical Aerospace Reports (STAR)
published by NASA Scientific and Technical
Information Facility
Post Office Box 8757
Baltimore/Washington International Airport
Maryland 21240, USA

Government Reports Announcements (GRA)
published by the National Technical
Information Services, Springfield
Virginia 22151, USA



Printed by Technical Editing and Reproduction Ltd
Harford House, 7-9 Charlotte St, London W1P 1HD

ISBN 92-835-1328-2